



## Physical Characteristics of Sulfur and Peroxide Cured EPDM Rubbers under Different Blowing Agent Concentrations

H.H. Hassan<sup>a</sup>, A.H. Al-Dardir<sup>a</sup>, J. A. Khaliel<sup>b</sup>, H. S. Ayoub<sup>a</sup>, Ashraf F. El-Sherif<sup>c</sup>,  
S.A. Khairy<sup>a</sup>, E.M. Abdel Barya<sup>d</sup>

<sup>a</sup> Department of Physics, Faculty of Science, Cairo University, Giza, Egypt

<sup>b</sup> Department of Physics, Faculty of Science, Misurata University, Misurata, Libya

<sup>c</sup> Laser Photonics Research CentDr, Engineering Physics Department,  
Military Technical College, Cairo, Egypt

<sup>d</sup> Department of Chemistry, Faculty of Science, Mansoura University, Mansoura, Egypt

### Abstract:

EPDM rubbers loaded with different concentration of azodicarbonamide as a foaming agent using two different cross-linking systems were subjected to the mechanical, compression and swelling tests at room temperature (300°K). Samples vulcanized by peroxide reveal more advantage over that vulcanized by sulfur especially for the amount of specific gravity and the compression test. The tensile test shows a noticeable increase in the true stress and strain at break for the sulfur cross-linking system than the peroxide one. For the swelling test, the empirical equation used by Kumnantip and Sombatsompop shows the best fitting for the degree of swelling – time data.

### Keywords:

EBDM Foam, mechanical properties, peroxide and sulfur vulcanizates, tensile resistance, Abrasion and swelling test.

### 1. Introduction

Foam rubbers are considered as key material in many important industries, such as, avionics, aerospace, mechanics and automotive. As the uses of foam rubbery materials increases, the need of synthesizing high quality elastomers with exceptional physical properties also increases. Foam rubbers are a set of elastomers formed by decomposition of blowing agent and thermal curing of rubber base material in presence of many additives. These additives provide many enhancements to the mechanical and physical properties of the cured rubber [1-3]. The most important additives are the vulcanization agents, which form the cross-linking between the chains of rubber and increase the tensile strength and hardness [4-6], and blowing agents that thermally decompose and provide trapped gaseous phase hence decreases rubber density. Moreover, the filler material that serves as mechanical properties enhancer. Some common additives like activators, accelerators and plasticizer are also used.

In response to this trend, we decided to study the effect of changing the concentration of azodicarbonamide foaming agent on the physical properties of both sulfur and peroxide cured EPDM foam rubber. We choose EPDM foam because of its great industrial importance and for its reliability in many everyday use products in our life. Beside EPDM rubber has resistance against many environmental conditions such as oxygen, ozone, heat and irradiation



[7-9]. We prepared a number of samples based on the recipes given by previous work on EBDM foam with different ingredients concentrations [10,11]. We also applied tensile, compression and swelling ASTM standard tests on the prepared samples.

## 2. Experimental

To study the effect of foaming agent on the mechanical properties of sulfur and peroxide cured EPDM rubber, we prepared two different master batches of EPDM samples with different concentration of azodicarbonamide as foaming agent. The first batch is made for sulfur cured EPDM and the second is for peroxide cured EPDM. The ingredients of samples are blended at room temperature on two-roll mill of 0.3m length and radius 0.15m diameter. The rotation rate of slow roll and gear ratio are 18 rpm and 1:4 respectively. Table 1 shows the ingredients of the prepared samples and the order of addition. After 24 hours, the sample was vulcanized and molded at temperature 150°C and pressure 15 MPa for 30 min.

Table.1: Ingredients of the prepared samples of sulfur and peroxide cured EPDM foamed rubber.

Substance	Ingredients (phr) <sup>a</sup>							
	Sulfur Cured EPDM Batch				Peroxide Cured EPDM Batch			
	Sample ES0	Sample ES5	Sample ES10	Sample ES15	Sample EP0	Sample EP5	Sample EP10	Sample EP15
EPDM	100	100	100	100	100	100	100	100
Stearic acid	2	2	2	2	2	2	2	2
ZnO	5	5	5	5	5	5	5	5
Paraffin oil	20	20	20	20	20	20	20	20
Silica	20	20	20	20	20	20	20	20
MBTS <sup>b</sup>	2	2	2	2	2	2	2	2
Sulfur	3	3	3	3	0	0	0	0
DCP <sup>c</sup>	0	0	0	0	3	3	3	3
ADC/K <sup>d</sup>	0	5	10	15	0	5	10	15

<sup>a</sup> parts per hundred parts of rubber by weight.

<sup>b</sup> Dibenzothiazyl disulfide.

<sup>c</sup> Dicumyl peroxide.

<sup>d</sup> Azodicarbonamide.

The samples were prepared on three standard forms: a) 0.2cm thick standard Die-D cut dumbbell shape strips for tensile test, b) 1.3cm thickness × 3cm diameter disks for compression, and c) 5cm × 2.5cm × 0.2cm sheets for swelling test. The densities of samples are mentioned in table 2.



Table 2: The measured densities of samples of sulfur and peroxide cured EPDM foamed rubber.

Sample name	$\rho$ (kg/m <sup>3</sup> )	Sample name	$\rho$ (kg/m <sup>3</sup> )
ES 0	1048 ± 4	EP 0	965 ± 4
ES 5	590 ± 3	EP 5	560 ± 3
ES10	570 ± 3	EP10	543 ± 3
ES15	544 ± 3	EP15	519 ± 3

Three standard tests were applied to the samples [13-15], which were shelf aged for 48 hours, to investigate their mechanical properties. These tests are according to ASTM standards number: D412–98a, D395–98 (method B) and D471- 98e1 for measuring tensile strength, compression and swelling of rubber samples, respectively. For the Test D 412–98a, the samples were tested by using a homemade standard tensile testing machine of the Polymer lab. at Physics Department, Faculty of Science, Cairo University.

### 3. Results and discussion

Figure (1) showed that the true tensile strength of the sulfur cured EPDM is higher than that cured by peroxide at almost zero ADC/K concentration. As the ADC/K concentration reaches 5 phr both EPDM types seemed to have the same value. At ADC/K concentrations of 10 and 15 phr, the value of sulfur cured EPDM lead once again as shown in figure 1a. The true strain at break of both EPDM types versus ADC/K concentration was similar to that of the true strength as shown in figure 1b.

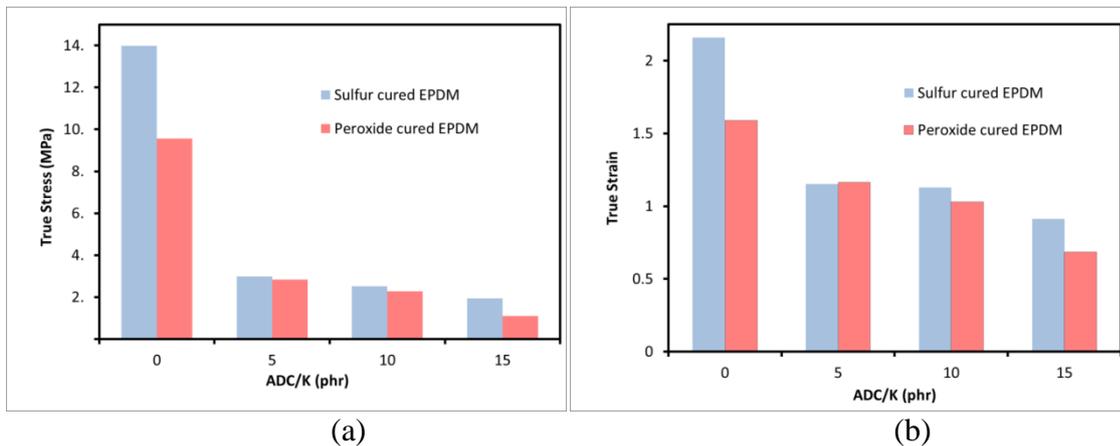


Fig.1 true stress (a) and true strain (b) values of sulfur cured and peroxide cured EPDM

Tensile tests reveal that the true stress-strain curve of the samples shows an explicit superiority of initial elastic modulus (Young’s modulus) for zero concentration ADC/K peroxide cured EBDM over all samples, this is due the strong carbon-carbon bond strength compared to the weaker sulfur –carbon bond [12].The values of elastic modulus of samples are presented in Table 3. On contrary, the break point of the zero concentration ADC/K sulfur cured EBDM sample was the highest among all samples as shown at figure 2a.

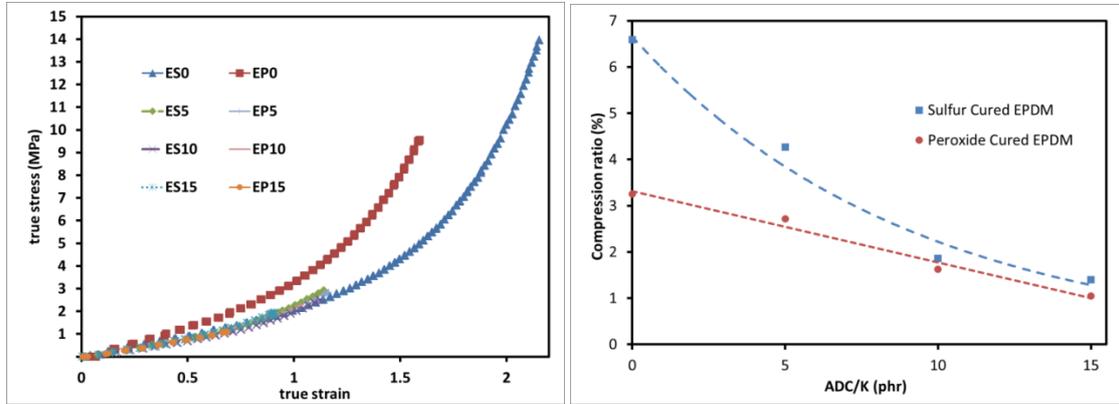


Fig.2 (a) true stress-strain curve for all samples (b) Compression ratio versus ADC concentration for both sulfur and peroxide cured samples.

Compression test shows an exponential behavior of compression ratio for sulfur cured EBDM samples with ADC/K concentration. Dissimilarly, for Peroxide cured EBDM samples, a linear behavior of compression ratio with ADC/K concentration is observed as shown in figure 2b.

Table 3: The elastic modulus of samples of sulfur and peroxide cured EPDM foamed rubber.

Sample name	$E$ (MPa)	Sample name	$E$ (MPa)
ES 0	1.87	EP 0	3.10
ES 5	1.56	EP 5	1.87
ES10	1.51	EP10	1.74
ES15	1.51	EP15	1.62

For swelling test, Xylene ( $(\text{CH}_3)_2\text{C}_6\text{H}_4$ ) was used as solvent for both sulfur and peroxide cured samples. As shown in figure (3), tests revealed that the degree of swelling for sulfur cured EBDM samples was higher than that of peroxide cured samples.

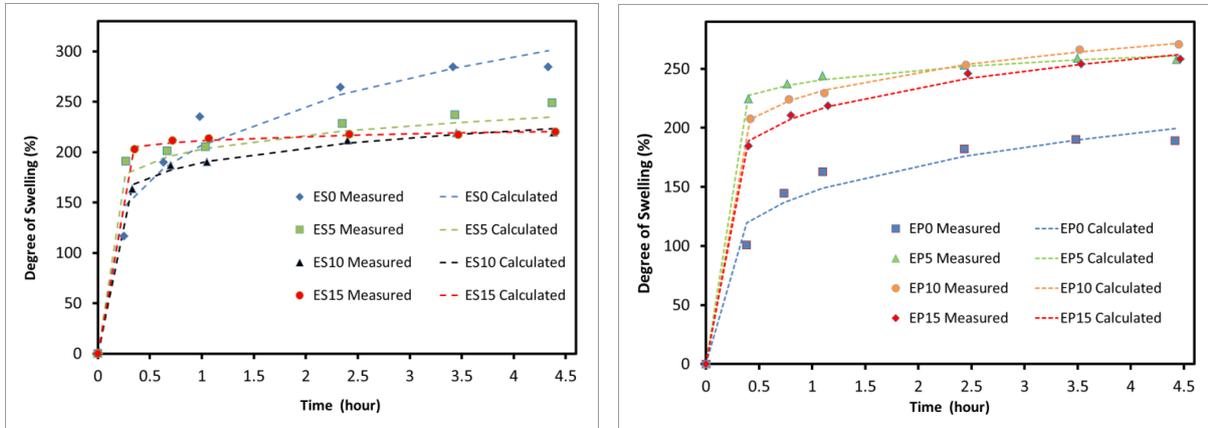


Fig.3 Percent change in samples mass versus time for (a) sulfur cured EBDM samples (b) peroxide cured EBDM samples

To model the swelling behavior of the tested sample versus time, we applied an empirical fitting equation used by Kumnuantip and Sombatsompop [16] in which the degree of swelling  $M_t$  is given by equation (1):

$$\frac{W_t - W_o}{W_o} \times 100 = M_t = M_\infty K t^n \quad (1)$$

Where  $W_o$  is the dry initial weight and  $W_t$  is the swollen weight after time  $t$ ,  $M_\infty$  is the degree of swelling at saturation,  $K$  and  $n$  are arbitrary fitting parameters determined by the least square method. Figure 4 shows the numerical values of  $K$  and  $n$  that matched the swelling behavior of all ADC/k sample concentrations.

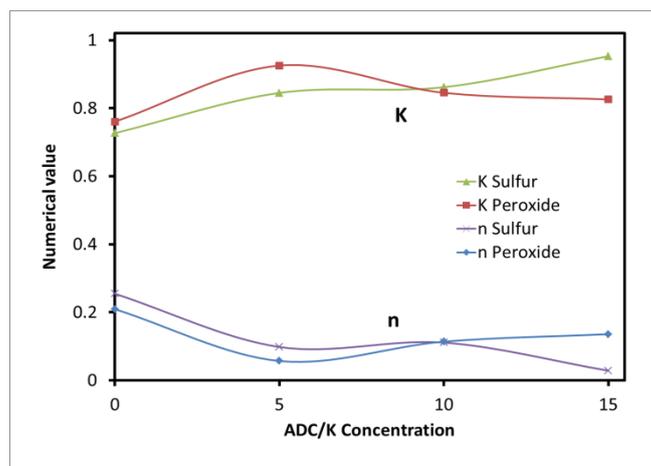


Fig.4 Values of K and n as a function of ADC/k concentration for all samples

It worth to mention that at ADC/k concentration of 10%, the value of  $K$  for sulfur cured samples intersected with that of the peroxide cured samples and an inflection of slopes



occurred. The same results were obtained for the value of  $n$  noting the small differences between both sample types.

#### **4. Conclusion**

The study reveals strong dependent of the investigated mechanical properties on the mentioned foaming agent concentration as discussed by other but relevant works. At 15 phr of ACD/K enhances the compressive properties of the samples especially for peroxide cured EPDM and decreases the degree of swelling for sulfur cured EPDM. The elastic modulus of peroxide cured EPDM is grater then sulfur cured EPDM for each same concentration of ACD/K .The obtained results represent a helpful knowledge boost for foam rubber based industrial applications.

#### **Acknowledgment**

The authors are very grateful to the members of physics department, faculty of science at Cairo University for their encouragement and helpful suggestions that made this work possible.

#### **References**

- [1] **Lin G, Zhang X-J, Liu L, Zhang J-C, Chen Q-M, Zhang L-Q.** Study on microstructure and mechanical properties relationship of short fibers/rubber foam composites. *European Polymer Journal*. 2004;40(8):1733-42.
- [2] **Wu YP, Ji MQ, Qi Q, Wang YQ, Zhang LQ.** Preparation, Structure, and Properties of Starch/Rubber Composites Prepared by Co-Coagulating Rubber Latex and Starch Paste. *Macromolecular rapid communications*. 2004;25(4):565-70.
- [3] **Zhang H-B, Yan Q, Zheng W-G, He Z, Yu Z-Z.** Tough graphene– polymer microcellular foams for electromagnetic interference shielding. *ACS applied materials & interfaces*. 2011;3(3):918-24.
- [4] **Cichomski E, Dierkes WK, Noordermeer JW, Schultz SM, Tolpekina TV, Reuvekamp L, et al.** Effect of the crosslink density and sulfur-length on wet-traction and rolling resistance performance indicators for passenger car tire tread materials. 2015.
- [5] **Zaimova D, Bayraktar E, Miskioglu I.** Design and manufacturing of new elastomeric composites: Mechanical properties, chemical and physical analysis. *Composites Part B: Engineering*. 2016;105:203-10.
- [6] **Naebpetch W, Junhasavasdikul B, Saetung A, Tulyapitak T, Nithi-Uthai N.** Influence of accelerator/sulphur and co-agent/peroxide ratios in mixed vulcanisation systems on cure characteristics, mechanical properties and heat aging resistance of vulcanised SBR. *Plastics, Rubber and Composites*. 2016;45(10):436-44.
- [7] **Eid MA, El-Nashar D.** Filling effect of silica on electrical and mechanical properties of EPDM/NBR blends. *Polymer-Plastics Technology and Engineering*. 2006;45(6):675-84.
- [8] **Arayaprane W, Rempel GL.** A comparative study of the cure characteristics, processability, mechanical properties, ageing, and morphology of rice husk ash, silica and carbon black filled 75: 25 NR/EPDM blends. *Journal of applied polymer science*. 2008;109(2):932-41.

**Military Technical College**

**Kobry Elkobbah,**

**Cairo, Egypt**

**April 3-5,2018**



**9<sup>th</sup> International Conference**

**on Mathematics and**

**Engineering Physics**

**(ICMEP-9)**

- [9] **Ismail H, Mathialagan M.** Comparative study on the effect of partial replacement of silica or calcium carbonate by bentonite on the properties of EPDM composites. *Polymer Testing*. 2012;31(2):199-208.
- [10] **El Lawindy AMY, El-Kade KMA, Mahmoud WE, Hassan HH.** Physical studies of foamed reinforced rubber composites Part I. Mechanical properties of foamed ethylene–propylene–diene terpolymer and nitrile–butadiene rubber composites. *Polymer international*. 2002;51(7):601-6.
- [11] **El Eraki M, El Lawindy A, Hassan H, Mahmoud W.** The physical properties of pressure sensitive rubber composites. *Polymer degradation and stability*. 2006;91(7):1417-23.
- [12] **Kruželák J, Sýkora R, Hudec I.** Sulphur and peroxide vulcanisation of rubber compounds–overview. *Chemical Papers*. 2016;70(12):1533-55
- [13] ASTM D412-98a, Standard Test Methods for Vulcanized Rubber and Thermoplastic Rubbers and Thermoplastic Elastomers-Tension, ASTM International, West Conshohocken, PA, 1998, [www.astm.org](http://www.astm.org)
- [14] ASTM D395-98, Standard Test Methods for Rubber Property-Compression Set, ASTM International, West Conshohocken, PA, 2001, [www.astm.org](http://www.astm.org)
- [15] ASTM D471-98e1, Standard Test Method for Rubber Property-Effect of Liquids, ASTM International, West Conshohocken, PA, 1999, [www.astm.org](http://www.astm.org)
- [16] **Obasi HC, Nwanonenyi S, Eze I, Chukwujike I, Anyiam C, Aguele F, et al.** Organic Solvents Transport Through Alkali-Treated Agro-waste Microfibre Incorporated with Low Density Polyethylene Composites. *American Journal of Polymer Science and Technology*. 2017;3(4):50-63.